

**RECOMMENDED PRACTICE
FOR
ACCELERATED STRENGTH
TESTING
AND
EVALUATION OF CONCRETE
FOR
ROAD AND AIRFIELD
CONSTRUCTIONS**



THE INDIAN ROADS CONGRESS

1983

MEMBERS OF THE SPECIFICATIONS AND STANDARDS COMMITTEE

1. K.K. Sarin (Convenor)	Addl. Director General (Roads), Ministry of Shipping & Transport
2. N. Sivaguru (Member-Secretary)	Chief Engineer (Roads), Ministry of Shipping & Transport
3. K.C. Alexander	Chief Engineer & Ex-officio Addl. Secy. to the Govt. of Kerala, P.W.D.
4. V.K. Arora	Chief Engineer (Roads), Ministry of Shipping & Transport
5. R.T. Atre	Secretary to the Govt. of Maharashtra (II) PW & H Deptt.
6. M.K. Chatterjee	Chief Engineer (Retd.) E.C. 164, Salt Lake, Calcutta.
7. D.C. Chaturvedi	Managing Director (Retd.) A-709 (H.I.G.), Indira Nagar, Lucknow.
8. Dr. M.P. Dhir	Deputy Director and Head, Roads Division, Central Road Research Institute
9. T.A.E. D'sa	Chief Engineer, The Concrete Association of India, Bombay
10. Y.C. Gokhale	Head, Flexible Pavements Division, Central Road Research Institute
11. I.C. Gupta	Engineer-in-Chief (Retd.) Haryana P.W.D., B&R
12. R.S. Gupta	Member (Engineering), Delhi Development Authority
13. A.Y. Gupte	Chief Road Engineer, Hindustan Petroleum Corporation Ltd., Bombay
14. D.P. Jain	Chief Engineer (Retd.), 0-21, Ashok Marg, Jaipur
15. M.B. Jayawant	Neelkanth, 24, Carter Road, Bandra, Bombay
16. D.C. Jha	Superintending Engineer (Design), C.D.O. Patna
17. N.H. Keshwani	Chief Engineer (Retd.) 797 DIII, Mandir Marg, New Delhi
18. Dr. S.K. Khanna	Prof. of Civil Engineering & Dean Development & Planning, University of Roorkee
19. S.B. Kulkarni	Bitumen Manager, Indian Oil Corporation Ltd. Bombay
20. P.K. Lauria	General Manager, Rajasthan State Bridge Construction Corporation Ltd., Jaipur
21. K.S. Logavinayagam	Chief Engineer, (Retd.) 181-B, 54th Street, Ashok Nagar, Madras
22. Mahabir Prasad	Chief Engineer (Retd.) 10/10 Sarojini Naidu Marg, Lucknow
23. H.C. Malhotra	Chairman & Managing Director, Engineering Projects (India) Ltd.
24. J.M. Malhotra	Secretary to the Govt. of Rajasthan P.W.D.
25. M.R. Malya	3, Panorama, 30, Pali Hill Road, Bombay
26. P.N. Misra	Engineer-in-Chief, (Retd.), U.P. PWD, B&R
27. I.K. Modi	Secretary, Gujarat B&C Deptt.
28. O. Muthachen	Engineer-in-Chief (Retd.), C.P.W.D. Poomkavil House, Somangalam, Punalur P.O. Kerala

**RECOMMENDED PRACTICE
FOR
ACCELERATED STRENGTH
TESTING
AND
EVALUATION OF CONCRETE
FOR
ROAD AND AIRFIELD
CONSTRUCTIONS**

Published by
THE INDIAN ROADS CONGRESS
Jamnagar House, Shahjahan Road,
New Delhi-110011
1983

(Price Rs.60/-
(Plus Packing & Postage)

IRC : 85-1983

First published : May, 1983

(Rights of Publication and of Translation are reserved)

RECOMMENDED PRACTICE FOR ACCELERATED STRENGTH TESTING AND EVALUATION OF CONCRETE FOR ROAD AND AIRFIELD CONSTRUCTIONS

1. INTRODUCTION

1.1. The quality acceptance criteria of most cement concrete works including paving concrete works for roads and airfields are based on the strength of specimens tested at the age of 28 days after curing under standard moist conditions. An estimate of 28-day strength of concrete is sometimes done from the corresponding 7-day strength results for purposes of early quality control. In case of many constructions, the time lapse of even 7 days is too long for the strength results to serve any useful purpose from the point of either quality control or predicting the 28-day strength.

1.2. With a view to overcoming this problem, accelerated strength testing of concrete has been recommended in this document that would provide an early information, say in about a day, on the concrete strength likely to be developed at 28 days. Such an information may enable taking decision on removal of any defective concrete very early while it has still not hardened much, or before it is covered by subsequent layer. It will thus help achieve better control of concrete quality economically with greatly reduced chances of rejection.

1.3. For predicting the compressive and flexural strengths of concrete at 7 or 28 days, it will be desirable to obtain in advance in the laboratory along with the mix design of concrete, the correlations between the accelerated strength results and standard cured strength results at 7 or 28 days, using the material to be actually used in construction. For evaluation of 28-day compressive strength of concrete through accelerated testing, the Indian Standards Institution has already laid down detailed specifications in IS:9013-1978. The present Recommended Practice relates

particularly to the 7 and 28-day flexural strength evaluation of concrete through accelerated curing. Since flexural strength of concrete is of great importance to the paving engineers, this document will have particular significance in road and airfield constructions.

1.4. A draft for the Recommended Practice was approved by the Cement Concrete Road Surfacing Committee in their meeting held at Lucknow on the 28th January, 1980 (personnel given below). This was considered by the Specifications and Standards Committee in their meeting held on the 28th May, 1981, when a Working Group consisting of P.C. Bhasin (Convenor), Dr. R.K. Ghosh, one representative of I.S.I., one representative of Cement Research Institute of India and Member-Secretary, Specifications and Standards Committee was set up to review the draft in light of the discussion held during the meeting. The Working Group held its meeting at New Delhi on the 5th August, 1981 and modified the draft, and later it was approved by the Specifications and Standards Committee in their meeting held on the 11th October, 1982.

K.K. Nambiar	...	<i>Convenor</i>
Dr. R.K. Ghosh	...	<i>Member-Secretary</i>

MEMBERS

Maj. Gen. S.S. Ahluwalia	N.V. Merani
Col. Avtar Singh	Y.R. Phull
Dr. K.L. Bhanot	G.S. Rao
H.S. Bhatia	M.D. Seth
D.C. Chaturvedi	Amarjit Singh
M.G. Dandavate	N. Sivaguru
Dr. M.P. Dhir	P.V. Somashekhar
P.K. Issac	S.D. Vidyarthi
P.J. Jagus	Director General, Cement
Maj. Gen. R.K. Kalra	Research Instt. of India
Dr. S.K. Khanna	City Engineer,
D.N. Khurana	Municipal Corporation of
P.J. Mehta	Bombay
Y.K. Mehta	The Director (Civil Engg.) ISI

The Director General (Road Development) &
Addl. Secretary to the Govt. of India — *Ex-officio*

This Recommended Practice was later approved by the Executive Committee and the Council in their meetings held on the 13th and 24th December, 1982 respectively.

2. SCOPE

2.1. This Recommended Practice covers procedure for accelerated curing, details of accelerated strength test under compression/flexure and evaluation therefrom of strength under standard curing for 7 or 28 days, and is recommended to be used when evaluation of 7 or 28-day flexural strength or both flexural and compressive strength is required from the accelerated strength tests.

2.2. For accelerated evaluation of 28-day compressive strength only, reference may be made to IS:9013-1978 "Method of Making, Curing and Determining Compressive Strength of Accelerated-cured Concrete Test Specimens", (para 5 -Accelerated curing by Boiling Water Method).

3. WORKING PRINCIPLE OF ACCELERATED CURING

The concrete specimens (cubes or beams) are cured in boiling water for $3.5 \text{ hours} \pm 5 \text{ min.}$ after $23 \pm \frac{1}{4} \text{ hours}$ of casting them. The specimens are tested after 2 hours of cooling in air under wet gunny bags. The total period elapsed between casting and testing is 28.5 hours.

4. APPARATUS FOR ACCELERATED CURING

4.1. Water Bath in the Laboratory

4.1.1. When it is desired to conduct accelerated strength test for both compression and flexure, the water bath which is to provide the accelerated curing conditions, shall consist of a galvanised steel tank of appropriate capacity and dimensions and shall have a detachable top cover. A tank should accommodate at a time 3 cubes and 3 beams encased in moulds. The plan of

placement of the moulds is shown in Fig. 1. The dimensions of the tank may be varied depending on the number, size and type of specimens to be accommodated in the tank.

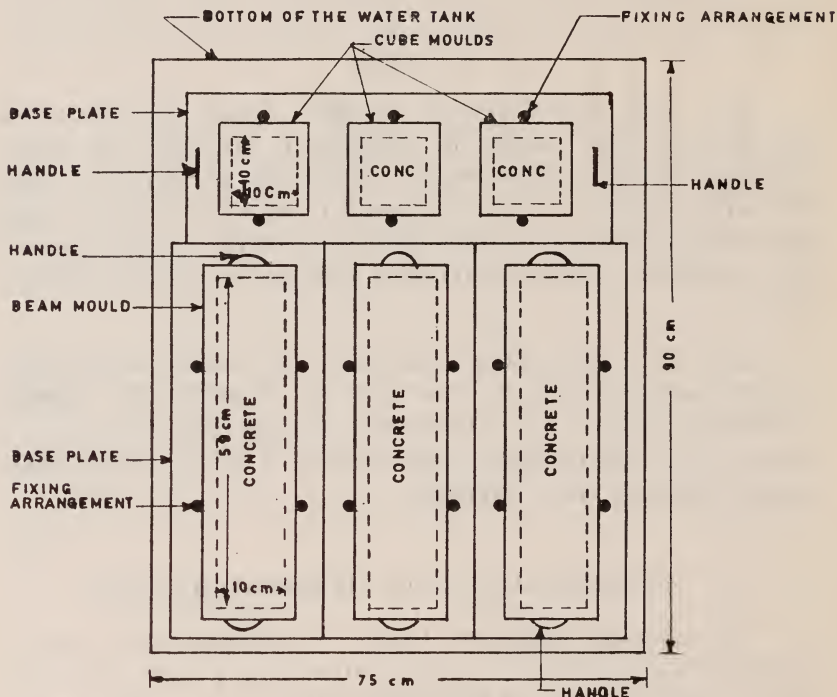


Fig. 1. Layout plan for 3 beams and 3 cubes inside the water tank

For $90\text{ cm} \times 75\text{ cm} \times 40\text{ cm}$ deep tank shown in Fig. 1, six immersion type heating elements (220V 1500W each) having a combined load of 9 kilo-watts are fitted horizontally at the side of the tank. These elements are distributed on the sides of the tank and located about 7 cm above the bottom of the tank. The tank is provided with a mild steel grid platform resting on 4 angle iron supports welded to the sides of the tank. The grid is placed about 10 cm above the bottom of the tank, Fig. 2. The cube and beam or only beam specimens together with their moulds are placed on the grid. The tank shall have an outlet at the bottom for emptying it, when required.

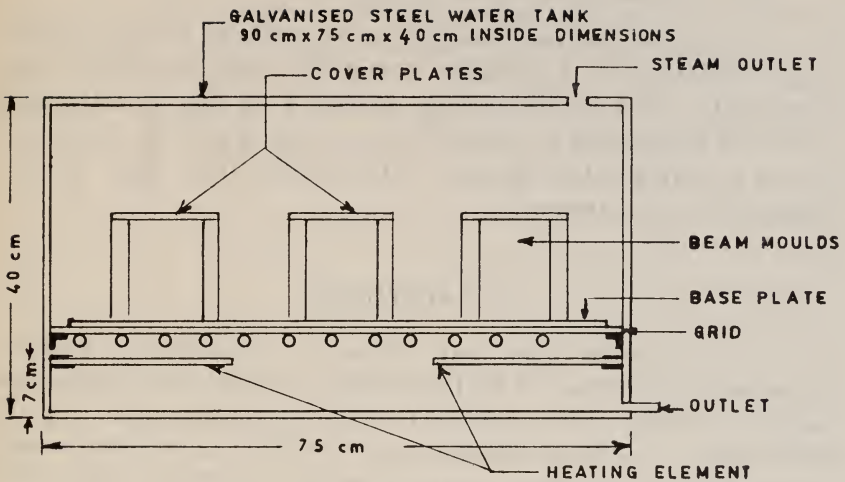


Fig. 2. Water tank showing position of heating elements, grid, base plate, mould, cover plate, etc.

4.1.2. The tank is to be filled with water to a depth of 25 cm for 90 cm \times 75 cm \times 40 cm deep tank so that when the specimens are placed in it, the water level rises to about 7 cm above the top of the moulds. This level of water is to be maintained during the heating period by adding small amount of water (as required) into the tank from time to time in order to maintain constant heat capacity of the curing medium. Depending on the ambient temperatures prevalent at the time of experimentation, about 60-75 minutes are required to raise the temperature of water in the tank to its boiling point near 100°C. The steam formed during heating is allowed to escape through an outlet provided in the tank cover, Fig. 2.

4 2. Water Bath in the Field

At construction sites in the field, where electrical power may not be available, water may be brought to boiling by means of heating through coal or firewood. The dimensions and other arrangements of the water bath should remain the same as described in para 4.1.

4.3. Mould for Concrete Specimens

The moulds for concrete specimens (cubes or beams) shall be as per IS:516-1959. In addition, 6 mm thick mild steel plate (with machined surface in contact with concrete) of size corresponding to that of the moulds is required to cover the specimens during the period of curing in boiling water. The moulds shall have suitable handles for easy removal.

5. PROCEDURE

5.1. Concrete cube and beam or only beam shall be prepared in accordance with IS:516-1959. The mould flanges are wiped clean after the concrete is trowelled level with the top of the mould. The specimens are cured for $23 \pm \frac{1}{4}$ hours under wet gunny bags at standard temperature ($27 \pm 2^\circ\text{C}$). After such curing, the specimens still in moulds shall be covered with cover plates (with machined surface in contact with concrete) and placed in boiling water in the tank. The temperature of water will drop slightly due to immersion of moulds but will regain the boiling temperature within 15 minutes.

5.2. The specimens shall be kept in the boiling water for 3.5 hours \pm 5 min. After this period, these should be removed from the tank with hooks having wooden handles, demoulded and left to cool in air for two hours under wet gunny bags. Immediately after 2 hours of cooling of the specimens, these shall be tested for compressive/flexural strength as per IS:516-1959.

6. EVALUATION OF 7 OR 28-DAY STRENGTH

6.1. Ordinarily, the correlation between the accelerated strength results as per procedure described in para 5 and standard cured strength results at 7 or 28 days shall be obtained in the laboratory along with the mix design of concrete, using the materials to be actually used in the construction. These correlations should be supplied to the site engineer along with the mix design.

6.2. Where such correlations are not made available from the laboratory, general guidance may be had from the correlations given in Figs. 3 and 4. While Fig. 3 gives the statistical correlations between accelerated and 7-day standard-cured compressive strength, Fig. 4 shows the same between accelerated and 7 or 28-day standard-cured flexural strength. In as much as the correlations between accelerated and 28-day standard-cured compressive strength are concerned, Fig. 2 of IS:9013-1978 may be followed. The correlations shown in Fig. 3 and 4 relate to concrete mixes using ordinary portland cements having widely different physical and chemical properties i.e., 3-day compressive strength varying between 160 and 235 kg/cm² and 7-day compressive strength varying between 225 and 330 kg/cm², specific surface varying between 3150 and 3720 cm² per gm (*Blaine's*), C₃S content varying between 28.4 per cent and 45.5 per cent and C₂S content varying between 41.5 per cent and 31.5 per cent, and different aggregates comprising Delhi quartzite, dense variety blast furnace slag from Bhilai and natural river gravel from Hardwar.

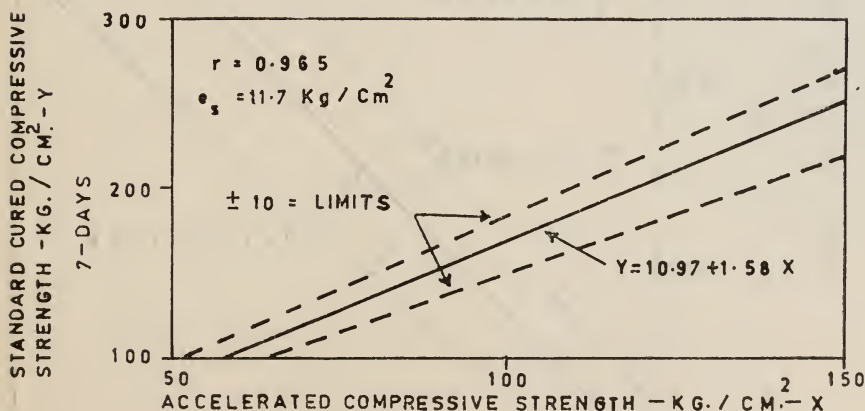


Fig. 3. Statistical relationship between accelerated and standard cured compressive strength

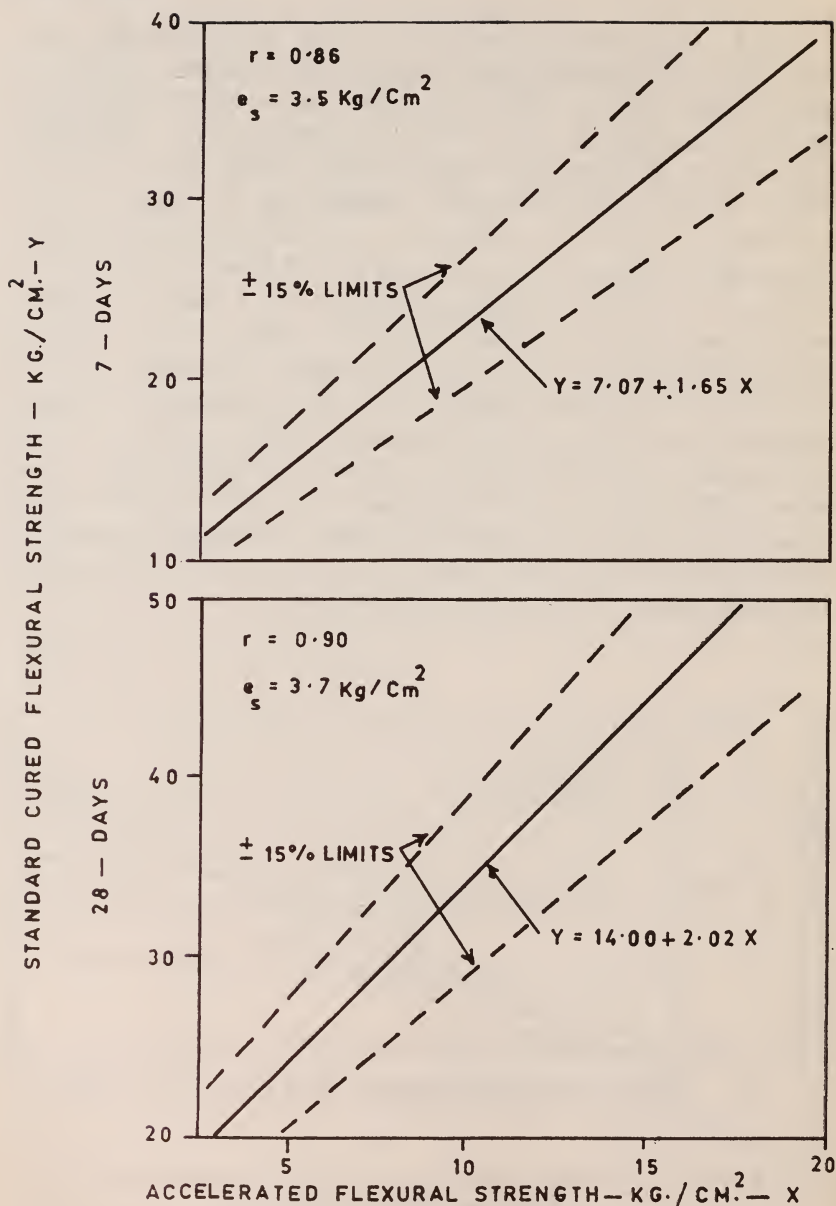


Fig. 4. Statistical relationships between accelerated and standard cured flexural strength

r = coefficient of correlation

e_s = standard error of estimate

29. P.K. Nagarkar Chief Engineer & Director, Maharashtra Engineering Research Institute
30. Lt. Gen. T.B. Nanda Master General of the Ordnance, Army Headquarters
31. K.K. Nambiar Chief Engineer (Retd.) Tamil Nadu, Ramanalaya, 11, First Crescent Park Road, Gandhinagar, Adyar, Madras
32. T.K. Natarajan Deputy Director and Head, Soil Mechanics Division, Central Road Research Institute
33. A.C. Padhi Chairman, Orissa Public Service Commission
34. Satish Prasad Manager, Indian Oil, AI-103, Safdarjung Enclave, New Delhi
35. Y.R. Phull Head, Rigid Pavements Division, Central Road Research Institute
36. Maj. Gen. J.M. Rai Director General Border Roads
37. Brig. L.V. Ramakrishna Director of Utilities, E-in-C's Branch, Army Headquarters
38. G. Raman Director (Civil Engineering), Indian Standards Institution, New Delhi
39. A.R. Rao Chairman, Bhubaneswar Regional Improvement Trust
40. Prof. N. Ranganathan Head, Traffic and Transportation Planning, School of Planning & Architecture
41. T.S. Reddy Project Co-ordinator, Central Road Research Institute
42. Dr. O.S. Saghal Principal Punjab Engineering College, Chandigarh
43. C.D. Thatte Director, Gujarat Engineering Research Institute
44. N. Sen Chief Engineer (Retd.) 12-A. Chittaranjan Park, New Delhi
45. R.P. Sikka Chief Engineer (Roads), Ministry of Shipping & Transport
46. L. Shivalingaiah Chief Engineer (Retd.) Karnataka P.W.D.
47. J.S. Sodhi Director, Quality Control, Punjab P.W.D. Chandigarh
48. Dr. N.S. Srinivasan Executive Director, National Transportation Planning & Research Centre, Trivandrum
49. G.M. Shonthu Chief Engineer, Kashmir, P.W.D. B&R
50. Prof. C.G. Swaminathan Director, Central Road Research Institute
51. B.T. Unwalla Chief Engineer (Retd.) 15/9, Rustom Baug, Sant Savta Marg, Byculia, Bombay-400 027
52. M.C. Vakil Superintending Engineer, H.P. PWD
53. The Director (B.D. Jayaraman) Highways Research Station, Madras
54. Brig. Gobindar Singh Director General (Road Development) & Addl. Secretary to the Govt. of India—Ex-officio

